

Magnon Heat Transport in $(\text{Sr},\text{La})_{14}\text{Cu}_{24}\text{O}_{41}$

C. Hess^{1,2}, C. Baumann^{1,2}, U. Ammerahl¹, B. Büchner^{2,1}, F. Heidrich-Meisner³, W. Brenig³, A. Revcolevschi⁴

¹ *II. Physikalisches Institut, Universität zu Köln, 50937 Köln, Germany*

² *II. Physikalisches Institut, RWTH Aachen, 52056 Aachen, Germany*

³ *Institut für Theoretische Physik, Technische Universität Braunschweig, 38106 Braunschweig, Germany*

⁴ *Laboratoire de Physico-Chimie, Université Paris-Sud, 91405 Orsay, France*

(February 1, 2008)

We have measured the thermal heat conductivity κ of the compounds $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ containing doped and undoped spin ladders, respectively. We find a huge anisotropy of both, the size and the temperature dependence of κ which we interpret in terms of a very large heat conductivity due to the magnetic excitations of the one-dimensional spin ladders. This magnon heat conductivity decreases with increasing hole doping of the ladders. The magnon heat transport is analyzed theoretically using a simple kinetic model. From this analysis we determine the spin gap and the temperature dependent mean free path of the magnons which ranges by several thousand Å at low temperature. The relevance of several scattering channels for the magnon transport is discussed.

Low-dimensional quantum magnets have attracted much attention in recent

years among both experimental and theoretical physicists. On the one hand these compounds serve as model systems for a comparison between experiment and theory, since exact solutions or numerical treatments of the model Hamiltonians yield clear-cut predictions. On the other hand unusual ground states and magnetic excitations are present, in particular in quasi-one-dimensional spin systems. A prominent example is the quantum disordered spin liquid state with a spin gap which is well established in frustrated and dimerized spin chains and in spin ladders [1–8].

Usually the magnetic excitations of these spin systems are experimentally studied by measuring spectroscopic or thermodynamic quantities which reveal information on the magnetic ground state and the excitation spectra as a function of energy and momentum. In principle, dispersive magnetic excitations should also contribute to a transport property, i.e. the thermal heat conductivity κ . The experimental investigation of the magnon heat transport could give interesting complementary information on the magnetic excitations, such as dissipation and scattering of magnons, similar as the study of electronic transport properties does in metals.

Recently, several studies of thermal heat conductivity in low dimensional spin systems have been performed and magnetic contributions to κ are discussed in one-dimensional spin systems such as e.g. CuGeO_3 [9–11] and Sr_2CuO_3 [12] as well as in two dimensional cuprates [13,14]. However, in many compounds the interpretation of the data is controversial, since an unambiguous discrimination of different contributions to κ is difficult or even impossible [15]. Very convincing experimental evidence for a magnon heat transport has been presented by Sologubenko *et al.* for $(\text{Sr},\text{Ca})_{14}\text{Cu}_{24}\text{O}_{41}$ [16]. The crystal structure of this compound contains two

quasi-one-dimensional magnetic subsystems along the c -axis. One subsystem is a sheet like arrangement of Cu_2O_3 two-leg ladders, where the Cu $S = \frac{1}{2}$ spins are strongly coupled via a Cu-O-Cu superexchange, while the other subsystem is an array of CuO_2 $S = \frac{1}{2}$ spin chains with weak magnetic interactions. While even the stoichiometric compound $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ is hole doped the holes are predominantly located in the chains [17,18]. Changing the composition i.e., the Sr, Ca, La content in $(\text{Sr},\text{Ca},\text{La})_{14}\text{Cu}_{24}\text{O}_{41}$, alters concentration and distribution of the holes. This results in drastic changes of the magnetic properties of the chains, whereas a large spin gap in the ladders of the order of 400 K is observed in all compounds [19–22]. However, the charge transport is determined by the holes in the ladders which are already present in $(\text{Sr},\text{Ca})_{14}\text{Cu}_{24}\text{O}_{41}$. Undoped ladders are only found in systems containing a large amount of trivalent ions, e.g. La.

In this paper we report on the thermal conductivity of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ parallel and perpendicular to the chain/ladder direction. In the undoped ladders of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ the magnon contribution is very large and exceeds the phonon contribution by nearly two orders of magnitude. A simple approach to describe the energy transport due to magnetic excitations in the ladders is presented.

We have grown single crystals of $\text{Ca}_{14}\text{La}_5\text{Cu}_{24}\text{O}_{41}$ and $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ by the traveling solvent floating zone method [23,24]. Using a standard steady state method measurements of κ have been performed on pieces cut along the principal axes with a typical length of 2 mm along the measuring direction and of about 0.5 mm for the two other directions. The thermal gradient has been determined with an Au/Fe-Chromel thermocouple.

Fig. 1 presents κ of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ as a function of temperature T measured along the three crystallographic axes (κ_a , κ_b , κ_c). A striking anisotropy of both, ab-

solite value and temperature dependence of the thermal conductivity is apparent. Only for the b -axis we find the qualitative behavior expected for phonon heat transport. At low T the occupation of phonon states implies an increase of the heat conductivity, whereas κ_b decreases at high T due to increased phonon scattering. κ_a deviates slightly from this usual phonon thermal conductivity of insulators (see inset of Fig. 1): At high temperature we find a slight increase with increasing T . This small increase of κ_a might be related to the complexity of the phonon spectrum and/or unusual scattering processes possibly related to the anomalous T dependence of the lattice constants [25]. We note that small deviations from the T dependence expected for the phonon heat transport as we observe for κ_a in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ are rather common for complex transition metal oxides. It is still possible and meaningful to discuss this data in the framework of a phonon heat conductivity κ_{ph} .

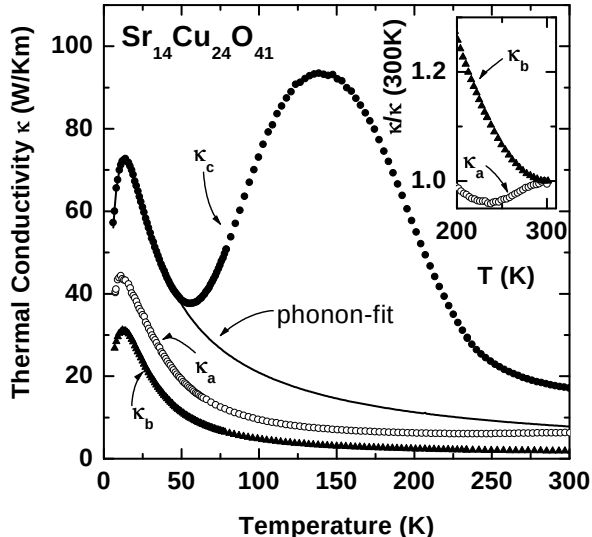


FIG. 1. Anisotropic thermal conductivity κ_a , κ_b and κ_c of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ as a function of temperature. Inset: κ_a and κ_b normalized to the value at 300 K.

This is impossible in the case of κ_c , i.e. for the heat transport along the chain/ladder direction in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$. In this case the phonon heat transport can only explain the data below ≈ 40 K where κ_c exhibits a low T maximum very similar to κ_a and κ_b . The absolute value is about 1.6 times larger than for κ_a . Since the velocity of sound and the elastic constants do not show a pronounced anisotropy [26] one has to attribute the anisotropy of κ_{ph} to anisotropic phonon scattering. Such an anisotropy of the phonon mean free path is also observed in other transition metal oxides [13,27] with low dimensional structure elements.

The most striking observation is the behavior of κ_c for temperatures above ≈ 40 K. With increasing T κ_c increases strongly and a second very pronounced maximum of the heat conductivity occurs at $T \simeq 140$ K. Further in-

creasing the temperature causes a sharp decrease of κ_c and for temperatures above 250 K the heat conductivity seems to saturate at a still rather large value of about 18 W/Km. Both the very large values of κ_c at intermediate T and the strange temperature dependence with the pronounced second maximum differ drastically from the usual κ_{ph} . We mention that our data for $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ agree qualitatively with those reported by Sologubenko *et al.* [16]. There are, however, strong deviations to the data of Kudo *et al.* [28] who report much smaller κ for all lattice directions and T probably due to enhanced defect scattering in their samples. Comparing our data for κ_c quantitatively with those in Ref. [16] reveals a perfect agreement for the low T maximum while the second peak is about 30% larger in our sample. At present we are systematically studying different crystals in order to understand the origin of these quantitative deviations.

As discussed in Ref. [16] it is reasonable to attribute the high temperature maximum of κ_c to magnetic excitations propagating along the spin ladders. The electronic heat transport as estimated from resistivity data and the Wiedemann-Franz-law is negligible. The T -dependence, anisotropy of κ and the absolute value of κ_c can not be explained by a phonon heat transport and the data for $\text{Ca}_{14}\text{La}_5\text{Cu}_{24}\text{O}_{41}$ allow also to exclude exotic electronic contributions as discussed below.

A determination and analysis of this very unusual magnon contribution requires a separation of a phonon background. Unfortunately, it is impossible to determine unambiguously the phonon background for $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$. For example, at high T the absolute values and T -dependence are unpredictable, which is clearly demonstrated by the qualitatively different behavior of κ_a and κ_b . Similar problems do exist at low T , since κ is determined by strongly anisotropic phonon scattering which can not be determined from independent experimental data or from theory. This means that any determination of the additional magnetic contribution in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ leads to a large error for low T and high T , i.e. for temperatures where the total κ is not much larger than κ_{ph} . In order to estimate the phonon background we fit the data at low temperatures $T \lesssim 40$ K with a Debye-model and extrapolate the behavior up to 300 K. The result of this description of κ_{ph} is indicated by a solid line in Fig. 1 which is much smaller than the measured κ in the entire temperature range above 50 K.

However, considering only the data for $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ one can question any non-phononic heat conductivity at $T \gtrsim 250$ K. A much more reliable separation of phonon and magnon heat transport is possible in the case of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ whose thermal conductivities along the a - and c -axes are shown in Fig. 2. At low T the thermal heat conductivity of this compound which contains undoped spin ladders and only slightly doped spin chains [17,18] is much smaller than in stoichiometric $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ for both directions. It is straightforward to attribute this isotropic suppression of κ_{ph} at low T to structural defects. On the one hand a lattice site is

occupied by randomly distributed Ca^{2+} and La^{3+} ions with strongly different sizes which is known to suppress κ_{ph} . On the other hand x-ray diffraction studies show structurally disordered chains in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$. Surprisingly, κ_c strongly increases above 40 K in spite of the structural disorder. At intermediate and high T κ_c is even larger than in stoichiometric $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and the room temperature value is comparable to that found in metals. In contrast to that a very small heat conductivity is found along the a -axis in the entire temperature range. Reduced size and T dependence are typical for κ_{ph} of a compound with many structural defects. It is apparent from Fig. 2 that this strong damping of κ_{ph} which is inferred from κ_a as well as from the low T behavior of κ_c enables a reliable determination of the additional contributions to κ_c above ≈ 40 K.

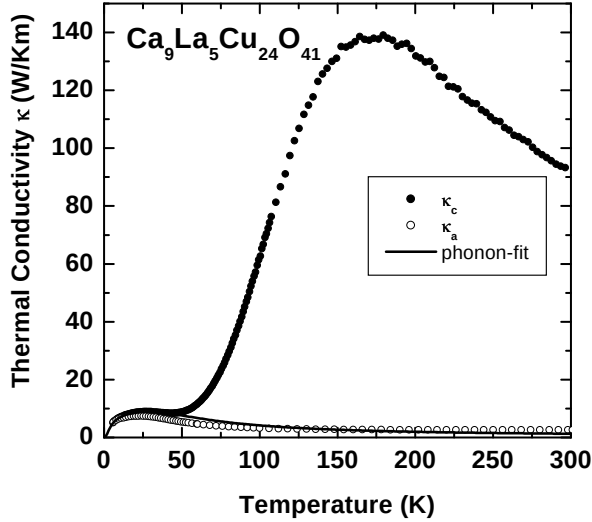


FIG. 2. Thermal conductivities of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ as a function of temperature measured along the a - and c -axes, κ_a and κ_c , respectively. The solid line represents an estimate of the phonon contribution to κ_c .

Before we turn to a quantitative analysis of κ_{mag} we mention several conclusions which can be drawn from the qualitative behavior of κ in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ and, in particular, from the comparison to the findings in the stoichiometric compound. The suppression of κ_{ph} which coincides with an enhancement of κ_c at high T gives very strong evidence that there are two independent

contributions to the heat transport. Moreover, some thinkable origins of the large additional contributions to κ_c in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ can be ruled out from the additional data. Excitations of the chains are irrelevant, since the magnetic and electronic properties of the heavily doped chains in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ showing charge order, spin gap and dimerization are completely different from the long range ordered chains in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ [29,30]. Heat transport due to collective electronic excitations as for example suggested for the thermal conductivity of the charge density wave compound $\text{K}_{0.3}\text{MoO}_3$ [31]

could be relevant in the strongly doped charge ordering $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ whereas it is certainly irrelevant in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ due to the strongly reduced hole content. Summarizing these arguments we have to state that the findings in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ strongly support the interpretation of the additional contribution to κ_c in terms of a magnon heat transport along the spin ladders. This magnon heat conductivity κ_{mag} is apparently not suppressed by structural disorder and, moreover, a smaller hole doping seems to enhance κ_{mag} at high T .

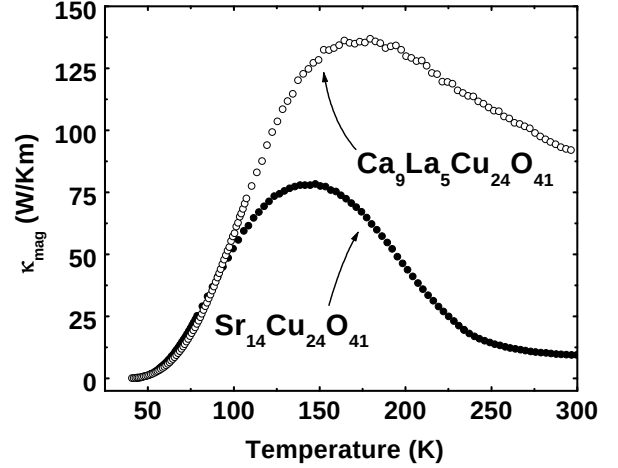


FIG. 3. Magnon thermal conductivities of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ and $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ as a function of temperature.

In Fig. 3 we show κ_{mag} for $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ which are derived by subtracting the Debye-fits of the phonon contribution from the measured κ_c . For $T \lesssim 100$ K absolute value and temperature dependencies of κ_{mag} are similar in the two compounds. However, pronounced differences occur at higher T . The magnetic heat conductivity on $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ κ_{mag} strongly decreases above ≈ 150 K. This decrease is much less pronounced and is found at higher temperature (above ~ 200 K) in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ where we find a very large $\kappa_{mag} \simeq 100$ W/Km even at room temperature.

In order to analyze the magnon heat transport theoretically we start from the simple kinetic expression

$$\kappa_{mag} = \frac{d}{dT} \sum_k v_k \epsilon_k n_k l_k \quad (1)$$

where v_k , ϵ_k , and l_k denote velocity, energy and mean free path of the magnetic excitations. Assuming a momentum independent mean free path, i.e. $l_k \equiv l_{mag}$ and using the distribution function

$$n_k = \frac{3}{3 + e^{\epsilon_k/k_B T}} \quad (2)$$

for the triplet excitations yields the following expression for the magnon heat conductivity:

$$\kappa_{mag} = \frac{3Nl_{mag}}{\pi \hbar k_B T^2} \int_{\Delta_{ladder}}^{\epsilon_{max}} \frac{\exp(\epsilon/k_B T)}{(\exp(\epsilon/k_B T) + 3)^2} \epsilon^2 d\epsilon. \quad (3)$$

Here, N is number of ladders per unit area and ϵ_{max} is the band maximum of the spin excitations which is at approximately 200 meV in $(\text{Sr,Ca,La})_{14}\text{Cu}_{24}\text{O}_{41}$. Note, that the distribution function (2) is different from a Bose distribution. This difference is used to account, on average, for the hard-core constraint of no on-site double-occupancy for the triplet excitations. While such a form of the distributions function would describe the occupation of a *local* triplet excitation exactly, it is only meant as an approximate phenomenology regarding the momentum space distribution - which is unknown for the present case. The primary motivation for of this type of a triplet distribution is to suppress unphysically large triplet densities at higher temperatures. From Eq. 3 it is apparent that the particular form of the magnon dispersion does not enter the heat conductivity of a one-dimensional triplet gas within a kinetic description - an effect which has not been noticed in other studies [16]. In particular, the momentum or energy dependence of the magnon velocity v which emerges from Eq. 1 plays no rôle in our approach. Note that the assumption of a k -independent mean free path implies a k -dependent scattering rate since v depends on the wave number. While this assumption seems reasonable for defect scattering more involved scenarios will apply in particular to inelastic scattering. Within our treatment the magnon heat

conductivity for experimentally relevant temperatures $T \ll \epsilon_{max}/k_B$ mainly depends on two parameters: the spin gap Δ_{ladder} and the mean free path l_{mag} . We mention, that (3) differs from an expression used by Sologubenko *et al.* [16] for the heat-conductivity of one-dimensional bosons not only by the distribution function (2) but also by an overall factor of three accounting for the triplet degeneracy.

For temperatures below 300 K κ_{mag} does not depend significantly on ϵ_{max} and in the following analysis of the data in the framework of Eq. 3 we use $\epsilon_{max} \simeq 200$ meV taken from the literature [21,32]. It is impossible, to determine reasonable values of the two remaining parameters l_{mag} and Δ_{ladder} by fitting the data with the expression in Eq. 3 without further assumptions. Therefore we ignore possible temperature dependencies of the spin gap and, moreover, assume a constant, temperature independent mean free path at low T , i.e. for a small number of thermally activated phonons and magnons. Knowing the spin gap from this first step of the analysis we can directly extract the temperature dependent l_{mag} from the data.

Our assumption of a constant l_{mag} at low T implies that the heat conductivity is determined by the temperature dependent activation of magnons in this temperature range. This is in agreement with the experimental data which roughly follow a simple activated behavior as displayed in Fig. 4. Note that Eq. 3 predicts deviations from the simple activation law and taking into account these corrections slightly improves the description of the data as demonstrated in Fig. 4. The spin gaps of $\Delta_{ladder} = 396$ K and $\Delta_{ladder} = 430$ K we obtain are in

fair agreement with the results from neutron scattering. We conclude that both, the temperature dependence of κ_{mag} and the absolute values of the spin gaps extracted from the data confirm our analysis. Comparing the left and right columns of Fig. 4 reveals that the agreement between data and theory is much better for $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ than for $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$. In the latter case a fair agreement with the theory at constant l_{mag} can only be obtained in a limited temperature range $55\text{K} \lesssim T \lesssim 85$ K. The deviations at higher temperatures, i.e. for $T \gtrsim 85$ K signal a significant temperature dependence of the mean free path, while the differences at low temperatures $T \lesssim 55$ K are most probably due to the uncertainty of the phonon heat conductivity which is much larger than κ_{mag} in this temperature range (see Fig. 1). The separation of κ_{mag} and κ_{ph} is much more reliable in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ and, indeed, the thermal conductivity for $T \lesssim 100$ K is well described by our model with constant l_{mag} .

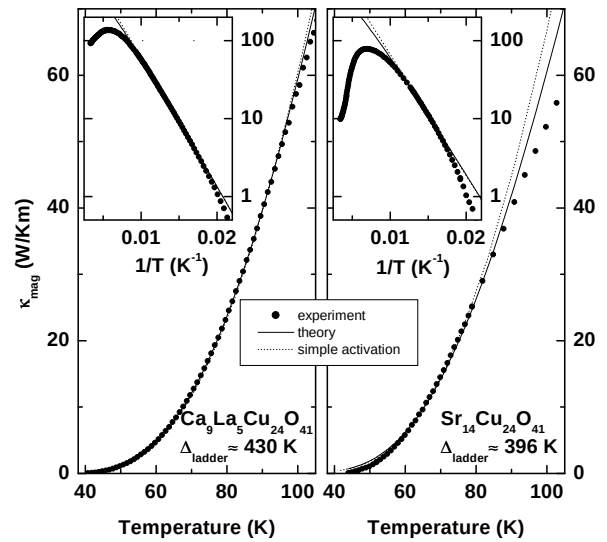


FIG. 4. Temperature dependence of the magnon thermal conductivities of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ (left) and $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ (right) at low temperatures in comparison with fit results to the data (Dotted lines: simple activation, solid lines: 1d-model for κ). Insets: Arrhenius representation of κ and fit results.

Based on the preceding analysis of the low temperature behavior of κ_{mag} it is possible to determine the temperature dependence of the mean free path l_{mag} (see Fig. 5). At low temperatures we find a very large l_{mag} of several thousand Å. Within the experimental uncertainty due to the phonon background we can not resolve differences of the low T saturation values of l_{mag} for the two compounds containing spin ladders with different hole content. There are, however, unambiguous and drastic differences at higher temperatures. In $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ which contains spin ladders with a rather large hole doping the magnon mean free path is much smaller and we find a rather strong temperature dependence between 85 K and 220 K. According to our analysis l_{mag} saturates for higher

temperatures and at $T = 300$ K the mean free path is about $60 \text{ \AA}$. While the saturation of l_{mag} above 220 K is clearly extractable from our data, the absolute values of κ_{mag} and l_{mag} strongly depend on the choice of the background, i.e. the extrapolation of κ_{ph} , and therefore a much smaller l_{mag} at 300 K is also compatible with the raw data in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$. For the second crystal with nearly undoped spin ladders a very large l_{mag} at room temperature is out of question. Our analysis yields a magnetic mean free path larger than $500 \text{ \AA}$ at 300 K. Moreover, the overall temperature dependent decrease of l_{mag} is less pronounced and deviations from the constant low T value start at higher temperatures than in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$.

Our results for l_{mag} in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ are in qualitative agreement with the findings reported by Sologubenko et al. [16]. There are, however, quantitative discrepancies due to the different theoretical description: for a given κ_{mag} our analysis leads to a smaller value of l_{mag} , mainly due to the more realistic distribution function for the magnetic excitations which we use in our approach (Eq. 2). Yet, the mean free paths which we extract from the analysis of our data are very large. In Ref. [16] it was speculated that holes are the main scatterers in the doped spin ladders of $(\text{Sr,Ca})_{14}\text{Cu}_{24}\text{O}_{41}$. This speculation is only partially supported by our results on a crystal with undoped spin ladders. At low T our data do not show a significant difference between the two crystals indicating that the very large l_{mag} at low temperature does not depend strongly on the hole content of the ladders. It is likely that the maximum magnon mean free path is determined by defects. Note however, that one has to discriminate between crystal defects and "magnetic defects", since there is no correlation between the maximum l_{mag} and the maximum phonon mean free path. The latter is much smaller in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ which is obvious from the damping of κ_{ph} at low T .

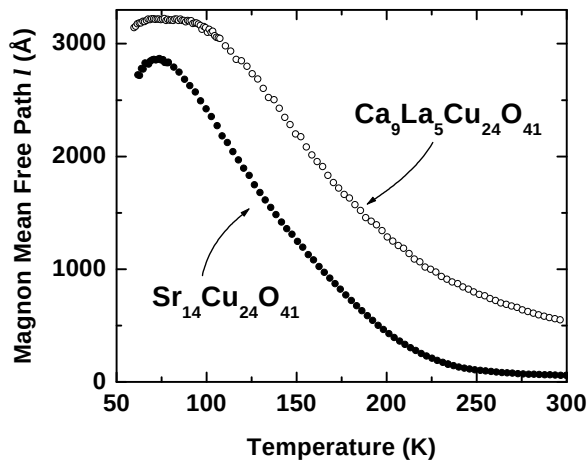


FIG. 5. Magnon mean free paths of $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$ (open symbols) and $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ (full symbols) as a function of temperature.

In contrast to the results at low T we do find a pronounced doping dependence of the magnon scattering at high T . The magnon mean free path is much smaller for the doped spin ladders of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and of the order of the mean hole distance in the ladders ($\approx 25 \text{ \AA}$) at 300 K [18]. In the same crystal resistivity measurements show a pronounced change of their temperature dependence at $T \simeq 220$ K. This anomaly which is frequently interpreted in terms of charge ordering is absent in $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$. Thus, one might argue that instead of the hole content, the hole mobility is crucial for the scattering of magnons, in order to explain the weak doping dependence of l_{mag} at low T and the strong differences at high T . Yet, holes and their mobility are not the only source of temperature dependent magnon scattering as demonstrated by our data for the crystal with undoped spin ladders. In this crystal we find a less pronounced, but qualitatively similar decrease of l_{mag} for $T > 100$ K. At room temperature the number of both, thermally excited magnons and phonons is already rather large. For example, the inverse density of magnons at 300 K as calculated for $\Delta_{ladder} = 430$ K can be interpreted as the "mean distance" of magnons and is already one order of magnitude smaller than l_{mag} . Further experimental and theoretical studies are necessary in order to determine the importance of magnon-defect, magnon-phonon and magnon-magnon scattering.

In summary we have measured the thermal conductivity of hole doped and undoped spin ladders realized in the compounds $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ and $\text{Ca}_9\text{La}_5\text{Cu}_{24}\text{O}_{41}$. In both cases we find a huge contribution to κ due to magnon heat transport. We have applied a simple kinetic approach to describe this contributions and have obtained the spin gaps of the ladders and the temperature dependence of the mean free path from our analysis. Obviously, at low T scattering of magnons on holes is rather ineffective since in this temperature region κ_{mag} of doped ladders is almost identical to κ_{mag} of the undoped ladders. For both we find a very large mean free path of magnons of several thousand $\text{\AA}$. At high T increased mobility of holes causes a strong damping of magnon heat transport in the hole doped ladders due to increased magnon-hole scattering whereas κ_{mag} in the undoped ladders only decreases slightly. This is reflected in the mean free path which in the former case at 300 K reduces to $l_{mag} \approx 60 \text{ \AA}$ which is in the same order of magnitude than the mean hole distance ($\approx 25 \text{ \AA}$). For undoped ladders $l_{mag} \approx 500 \text{ \AA}$ at 300 K. This large value is one order of magnitude larger than the inverse density of magnons at this temperature and might indicate only weak magnon-magnon scattering effects.

This work was supported in part by the Deutsche Forschungsgemeinschaft through SFB 341 and SP 1073 as well as under Grant No. BR 1084/1-1 and BR 1084/1-2.

- [1] E. Dagotto, T.M. Rice, *Science* **271**, 618 (1996).
- [2] T.M. Rice, *Z. Phys. B* **103**, 165 (1997).
- [3] T.M. Rice, *Physica B* **241-243**, 5 (1998).
- [4] E. Dagotto, *Rep. Prog. Phys.* **62**, 1525 (1999).
- [5] D.C. Johnston, R.K. Kremer, M. Troyer, X. Wang, A. Klümper, S.L. Bud'ko, A.F. Panchula, and P.C. Canfield, *Phys. Rev B* **61**, 9558 (2000).
- [6] D.C. Johnston, M. Troyer, S. Miyahara, D. Lidsky, K. Ueda, M. Azuma, Z. Hiroi, M. Takano, M. Isobe, Y. Ueda, M.A. Korotin, V.I. Anisimov, A.V. Mahajan, and L.L. Miller, *cond-mat/0001147*
- [7] S. Sachdev, *Science* **288**, 475 (2000).
- [8] A. Klümper and D.C. Johnston, *Phys. Rev. Lett.* **84**, 4701 (2000)
- [9] Y. Ando, J. Takeya, D.L. Sisson, S.G. Doettinger, I. Tanaka, R.S. Feigelson, and A. Kapitulnik, *Phys. Rev. B* **58**, R2913 (1998).
- [10] A.N. Vasil'ev, V.V. Pryadun, D.I. Khomskii, G. Dhahlenne, A. Revcolevschi, M. Isobe, and Y. Ueda, *Phys. Rev. Lett.* **81**, 1949 (1998).
- [11] J. Takeya, I. Tsukada, Y. Ando, T. Masuda, K. Uchinokura, *Phys. Rev. B* **62**, R9260 (2000).
- [12] A.V. Sologubenko, E. Felder, K. Giannò, H.R. Ott, A. Vietkine, and A. Revcolevschi, *Phys. Rev. B* **62**, R6108 (2000).
- [13] Y. Nakamura, S. Uchida, T. Kimura, N. Motohira, K. Kishio, K. Kitazawa, T. Arima, and Y. Tokura, *Physica C* **185-189**, 1409 (1991).
- [14] J.L. Cohn, C.K. Lowe-Ma, and T.A. Vanderah, *Phys. Rev. B* **52**, 13134 (1995).
- [15] Hofmann, H. Kierspel, T. Lorenz, G. S. Uhrig, O. Zabara, A. Freimuth, H. Kageyama, Y. Ueda, *cond-mat/0103012*
- [16] A. V. Sologubenko, K. Giannò, H.R. Ott, U. Ammerahl, and A. Revcolevschi, *Phys. Rev. Lett.* **84**, 2714 (2000).
- [17] T. Osafune, N. Motoyama, H. Eisaki, and S. Uchida, *Phys. Rev. Lett.* **78**, 1980 (1997).
- [18] N. Nücker, M. Merz, C.A. Kuntscher, S. Gerhold, S. Schuppler, R. Neudert, M. S. Golden, J. Fink, D. Schild, S. Stadler, V. Chakarian, J. Freeland, Y.U. Idzerda, K. Conder, M. Uehara, T. Nagata, J. Goto, J. Akimitsu, N. Motoyama, H. Eisaki, S. Uchida, U. Ammerahl, and A. Revcolevschi, *Phys. Rev. B* **62**, 14384 (2000).
- [19] K.I. Kumagai, S. Tsuji, M. Kato, and Y. Koike, *Phys. Rev. Lett.* **78**, 1992 (1997).
- [20] K. Magishi, S. Matsumoto, Y. Kitaoka, K. Ishida, K. Asayama, M. Uehara, T. Nagata, and J. Akimitsu, *Phys. Rev. B* **57**, 11533 (1998).
- [21] R. S. Eccleston, M. Uehara, J. Akimitsu, H. Eisaki, N. Motoyama, S. Uchida, *Phys. Rev. Lett.* **81**, 1702 (1998).
- [22] S. Katano, T. Nagata, J. Akimitsu, M. Nishi, and K. Kakurai, *Phys. Rev. Lett.* **82**, 636 (1999).
- [23] U. Ammerahl, G. Dhahlenne, A. Revcolevschi, J. Berthon, H. Moudde, *Journal of Crystal Growth* **193**, 55 (1998).
- [24] U. Ammerahl, A. Revcolevschi, *Journal of Crystal Growth* **197**, 825 (1999).
- [25] U. Ammerahl, B. Büchner, L. Colonescu, R. Gross, and A. Revcolevschi, *Phys. Rev. B* **62**, 8630 (2000).
- [26] D. König, U. Löw, S. Schmidt, H. Schwenk, M. Sieling, W. Palme, B. Wolf, G. Bruls, B. Lüthi, M. Matsuda, K. Katsumata, *Physica B* **237-238**, 117 (1997).
- [27] C. Hess, B. Büchner, M. Hücker, R. Gross, and S-W. Cheong, *Phys. Rev. B* **59**, 10397 (1999); D. Cassel, C. Hess, B. Büchner, M. Hücker, R. Gross, O. Friedt, and S-W. Cheong *J. Low Temp. Phys.* **117**, 1083 (1999).
- [28] K. Kudo, S. Ishikawa, T. Noji, T. Adachi, Y. Koike, K. Maki, S. Tsuji, and K. Kumagai, *J. Phys. Soc. Jpn.* **70**, 437 (2001).
- [29] M. Matsuda, K.M. Kojima, Y.J. Uemura, J.L. Zarestky, K. Nakajima, K. Kakurai, T. Yokoo, S.M. Shapiro, and G. Shirane, *Phys. Rev. B* **57**, 11467 (1998).
- [30] U. Ammerahl, B. Büchner, C. Kerpen, R. Gross, and A. Revcolevschi, *Phys. Rev. B* **62**, R3592 (2000).
- [31] Ž. Bihar, D. Starešinić, K. Biljaković, and T. Sambongi, *Europhys. Lett.* **40**, 73 (1997).
- [32] M. Matsuda, K. Katsumata, R.S. Eccleston, S. Brehmer, and H.J. Mikeska, *Phys. Rev. B* **62**, 8903 (2000).